Section A-Research paper



AN INVESTIGATION INTO THE USE OF WASTE PLASTIC AND CRUMB RUBBER IN BITUMINOUS PAVING MIXTURES

AUTHOR : ZUBAIR AHMAD BHAT , M.tech student at Rayat Bahra University , Punjab ,India

Email : <u>bhatzubair7@gmail.com</u>

AUTHOR : E.R AJAY VIKRAM

Asst. Professor ,Dept.of civil Engineering at Rayat Bahra University ,Punjab ,India

doi: 10.48047/ecb/2023.12.si4.1163

ABSTRACT

Generation of plastic waste and rubber waste is increasing day by day and the necessity to dispose of this waste in a proper way is arising. Nowadays pavements are subjected to various kinds of loading which affects the pavement performance condition that causes various distresses. Use of plastic and rubber in pavement design as an innovative technology not only strengthened the road construction but also increase the road life. In this study, different tests were conducted on aggregates, bitumen, and bituminous mixes. The effect of the addition of waste polyethylene in the form of locally available carry bags had been checked on aggregates as well as on bitumen. As per visual inspection, 5%, 7.5% and 10% plastic coating was made on aggregates and sample were checked for crushing, impact and abrasion values. Effect of addition of waste plastic and crumb rubber on bitumen had been studied by varying concentrations of polyethylene from 0% to 15% i.e. 0%, 5%, 7.5%, 10%, 12.5% and 15% in bitumen. Various tests such as penetration, ductility, softening point, flash and fire point, viscosity and loss on heating were performed on the samples. The optimum percentage was taken from these tests which had shown satisfactory results for all the tests performed. Later, that optimum percentage value was used for preparing bituminous mixes for testing pavement properties such as Marshall Stability, compressive strength, and indirect tensile strength. As per the test results, about 10% plastic waste with crumb rubber replacement in bitumen shows better results than conventional bitumen as well as 10% plastic coating to aggregates also improve the load-bearing capacity. The strength is found to be increased by 62% as compared to conventional mixes. By using plastic waste in flexible pavement design, the problem of plastic and waste rubber disposal gets solved as well as the performance of roads gets improved. Investigations can also be made on using other grades of bitumen and other substituents. Generation of plastic waste and rubber waste is increasing day by day and the necessity to dispose of this waste in a proper way is arising. Nowadays pavements are subjected to various kinds of loading which affects the pavement performance condition that causes various distresses. Use of plastic and rubber in pavement design as an innovative technology not only strengthened the road construction but also increase the road life. In this study, different tests were conducted on aggregates, bitumen, and bituminous mixes. The effect of the addition of waste polyethylene in the form of locally available carry bags had been checked on aggregates as well as on bitumen. As per visual inspection, 5%, 7.5% and 10% plastic coating was made on aggregates and sample were checked for crushing, impact and abrasion values. Effect of addition of waste plastic and crumb rubber on bitumen had been studied by varying concentrations of polyethylene from 0% to 15% i.e. 0%, 5%, 7.5%, 10%, 12.5% and 15% in bitumen. Various tests such as penetration, ductility, softening point, flash and fire point, viscosity and loss on heating were performed on the samples. The optimum percentage was taken from these tests which had shown satisfactory results for all the tests performed. Later, that optimum percentage value was used for preparing bituminous mixes for

testing pavement properties such as Marshall Stability, compressive strength, and indirect tensile strength. As per the test results, about 10% plastic waste with crumb rubber replacement in bitumen shows better results than conventional bitumen as well as 10% plastic coating to aggregates also improve the load-bearing capacity. The strength is found to be increased by 62% as compared to conventional mixes. By using plastic waste in flexible pavement design, the problem of plastic and waste rubber disposal gets solved as well as the performance of roads gets improved. Investigations can also be made on using other grades of bitumen and other substituents.

Keywords— Pavement, Bitumen, Waste plastic, Crumb rubber, Plastic coated aggregate

1. INTRODUCTION

Plastic and rubber are everywhere in today's lifestyle. The main problem is what to do with waste. Use of plastic waste which is non-biodegradable is rapidly growing and researchers have found that the material can remain on earth for 4500 years unchanged and without degradation. Plastic and rubber are very versatile material. Due to the industrial revolution, and its large scale production they seemed to be a cheaper and effective raw material. Today, every vital sector of the economy starting from agriculture to packaging, automobile, electronics, electrical, building construction, communication sectors has been virtually revolutionized by the applications of plastics and rubbers. Several studies carried out by Health Departments have proven the health hazard caused by improper disposal of plastic waste and rubber waste . The health hazard includes reproductive problems in human and animal, genital abnormalities etc. Although the waste plastic and rubber taking the face of the devil for the present and future generation, we can't avoid the use of plastic and rubber but we can reuse it. This threat of disposal of plastic and rubber will not solve itself and certain practical steps have to be initiated at the ground level. On the other hand, the road traffic is increasing with time hence there arises a need to increase the load bearing capacities of roads which can be made possible by utilizing the waste plastic and crumb rubber in flexible pavement design .

1.1 Necessity

Use of polyethylene in road construction is not new. Some aggregates are highly hydrophilic (water-loving). Like bitumen, polyethylene is hydrophobic (water-hating) in nature. So the addition of hydrophobic polymers by dry or wet mixing process to asphalt mix lead to improvement of strength, water repellent property of the mix. Polymer modification can be considered as one of the solutions to improvise the fatigue life, reduce the rutting & thermal cracking in the pavement. Creating a modified bituminous mixture by using recycled polymers (e.g., polyethylene) which enhances properties of HMA mixtures would not only produce a more durable pavement but also provide a beneficial way of disposal of a large number of recycled plastics . Crumb rubber obtained from the shredding of those scrap tire has been proven to enhance the properties of plain bitumen since the 1840's. It can be used as cheap and environment-friendly modification process to minimize the damage of pavement due to increase in service traffic density, axle loading and low maintenance services which deteriorated and subjected road structure to failure more rapidly.

- Stronger road with increased Marshall Stability value.
- Better resistance towards rainwater and water stagnation so no stripping and no potholes.
- Increase binding and better bonding of the mix thus reduction in pores in aggregate.
- No leaching of plastics.
- No effect of radiation like UV
- The load withstanding property increases. It helps to satisfy today's need for increased road transport

2. LITERATURE REVIEW

The concept of using plastic and rubber in flexible pavement has been done several years ago in India.

Plastic has played a very vital role in increasing the strength of bitumen as well as aggregate. Prof. C. E. G. Justo (2015) states that the addition of plastic in bitumen improves the stability, strength, life and other desirable properties of bitumen.[1] Similarly, Dr R. Vasudevan (2013) states that the polymer bitumen blend is a better binder compared to plain bitumen.[2]Dr. Khandekar S.D. et al. (2015)stated that the concept of utilization of waste plastic in the construction of pavement has shown better resistance to water which reduces the stripping of bitumen from aggregate and also made investigations over the use of waste plastic in road construction as an effective way to reutilize the plastic waste.[3] Nemade S. et al. (2013) studied the feasibility of the use of shredded waste plastics in semi- dense bituminous concrete with 60/70 penetration grade bitumen employing the dry process of mixing. On heating, the softened plastics, provide a thin coating on the aggregate. Marshall Stability and flow values, over 50 samples with varying percentage bitumen by weight of mix and percentage plastics by weight of binder were evaluated. There was a 10% saving in the bitumen content which leads to a saving in the national economy and also an eco-friendly method for the disposal of waste plastics. The stability value of the mix was increased by about 30%. There is also less ageing of bitumen and no bleeding. The plastic coated aggregates showed no stripping even after 96 hours of water immersion and hence avoid the use of anti-stripping agents in bituminous mixes. Water absorption was found to be less as compared to uncoated aggregates indicating its higher degree of water susceptibility.[4] Mohd Rasdan Ibrahim (2013) explains that Crumb rubber modification has been proven to enhance the properties of pure bitumen. Crumb rubber modifications of bitumen have been proven to improve characteristics of bituminous binder such as the viscosity, softening point, loss modulus, and storage modulus. This subsequently improves the rutting resistance, resilience, and improving fatigue cracking resistance of asphaltic mixes. In order to achieve a superior and balanced CRMB in term of high and low-temperature properties, factors such as the mixing time, temperature, characteristics, and source of the crumb rubber and bitumen type must be considered since these are the factors that govern the resulting performance of asphaltic mixes. Ageing mechanism of CRMB is also important to be considered in order that the resulting CRMB has a workable viscosity to be applied in the construction process. Finally, chemical modification of CRMB is a new area that has promising possibilities in the future to further enhance the properties of CRMB and at the same time eliminate rubber particle settling problem that is one of the limiting factors in the current application of crumb rubber modified bitumen [5].

3. RESEARCH METHODOLOGIES

The research methodology for the present study has adopted various tests to investigate the results on aggregate, bitumen and waste plastic with crumb rubber substituted bitumen and aggregate-bitumenmodified mix. The waste plastic and crumb rubber are mixed in equal proportion. The waste plastic has been collected from the neighborhood college area and crumb rubber is obtained from the tyre industry and used for testing. The various tests conducted on bitumen and modified bitumen was as follows:

| S | Tes | Apparatus used | Reference | |
|-----|------------------|-----------------------|-------------------|--|
| no. | t | | | |
| 1. | Penetration Test | Standard Penetrometer | IS : 1203-1978 | |
| 2. | Ductility Test | Ductility Apparatus | IS: 1208-1978 | |
| 3. | Softening Point | Ring Ball Apparatus | IS: 1205-1978 | |
| 4. | Flash And Fire | Pensky-Martens | IS : 1209-1978 | |
| | Point | Apparatus | | |
| 5. | Viscosity Test | Orifice Viscometer | IS: 1206(Part I)- | |
| | | | 1978 | |
| 6. | Loss On Heating | Oven | IS : 1212-1978 | |

For checking whether the plastic coating can be used to enhance the strength of aggregates, the following tests were conducted on aggregates and plastic coated aggregates:

| S | Tes | Apparatus used | Reference |
|-----|------------------|------------------------------|------------------------|
| no. | t | | |
| 1. | Aggregate Impact | Impact Testing Machine | IS: 2386(Part IV)-1963 |
| | Value | | |
| 2. | Abrasion Value | Los Angeles Abrasion Testing | IS: 2386(Part IV)-1963 |
| | | Machine | |
| 3. | Crushing Value | Crushing Value Apparatus | IS: 2386(Part IV)-1963 |

| Table 2: | Tests | on | aggregates |
|----------|-------|----|------------|
|----------|-------|----|------------|

The optimum percentage of plastic and crumb rubber substitution is found out from bitumen testing. Various bituminous mixes were prepared by using pure bitumen and plastic and crumb rubber substituted bitumen. These mix samples were tested for the following tests:

| | Table 5. Tests on aggregates | | | | | | | | |
|-----|------------------------------|-------------------|---------------------------|--|--|--|--|--|--|
| S | Tes | Apparatus used | Referen | | | | | | |
| no. | t | | ce | | | | | | |
| 1. | Marshall Stability Test | Marshall Test | IRC SP 53-1999 and ASTM D | | | | | | |
| | | Apparatus | 1559-1979 | | | | | | |
| 2. | Compressive Strength | Universal Testing | ASTM D 1074-09 | | | | | | |
| | Test | Machine | | | | | | | |
| 3. | Indirect Tensile Strength | Universal Testing | ASTM D 6931 | | | | | | |
| | Test | Machine | | | | | | | |

Table 3: Tests on aggregates

4. RESULT AND DISCUSSION

4.1 Laboratory tests on Aggregates

The results of various tests conducted over aggregates are as follows:

Table 4: Results of tests on aggregates

| S no. | Tes | Result | | | | Standa | |
|-------|----------------|-----------|-------|-------|-------|----------|--|
| | t | | (%) | | | | |
| | | Pure | Value | | | | |
| | | aggregate | Coat | Coat | Coat | | |
| 1. | Crushing Value | 21.72 | 19.57 | 17.18 | 16.45 | 30 % Max | |
| 2. | Impact Value | 13.46 | 12.50 | 10.90 | 8.92 | 30 % Max | |
| 3. | Abrasion Value | 9.8 | 9 | 8.4 | 7.6 | 30 % Max | |

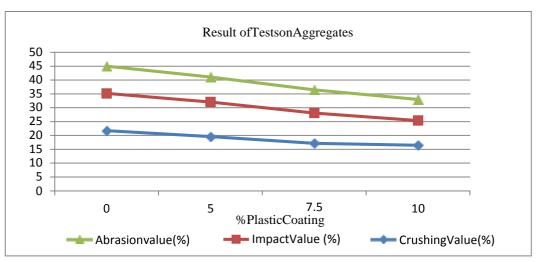


Fig. 1: Results of tests on aggregates

Comment: The strength of aggregates gets increased after coating with plastic which is beneficial in the pavement.

4.2 Laboratory tests on Bitumen

The results of various tests conducted on bitumen are as follows:

| | | Resul | | | | | | |
|---------|-----------------|---------------|---------|--------------------------|-------------------|-------------------|---------|---------|
| S no. t | | | | | | | | |
| | | Penetrati | Ductili | Soft. | Flas | Fire | Viscosi | Loss on |
| | | on | ty | Pt.(⁰ | h | pt.(⁰ | ty | Heating |
| | | (mm) | (cm) | C) | pt.(⁰ | C) | (sec) | (%) |
| | | | | | C) | | | |
| 1. | Pure Bitumen | 84 | 81 | 46 | 248 | 291 | 290 | 0.32 |
| 2. | 5% Replacement | 79 | 62 | 48 | 257 | 300 | 190 | 0.21 |
| 3. | 7.5% | 73 | 51 | 54 | 265 | 310 | 165 | 0.16 |
| | Replacement | | | | | | | |
| 4. | 10% Replacement | 65 | 47 | 62 | 280 | 330 | 155 | 0.21 |
| 5. | 12.5% | 60 | 38 | 65 | 290 | 350 | 132 | 0.25 |
| | Replacement | | | | | | | |
| 6. | 15% Replacement | 58 | 32 | 69 | 297 | 360 | 121 | 0.27 |
| | Standard Values | 60 | 50 | 40 | 220 | 290 | 50 | 1% |
| | | Min | Min | Min | Min | Min | Min | Max |

Table 5: Results of tests on bitumen

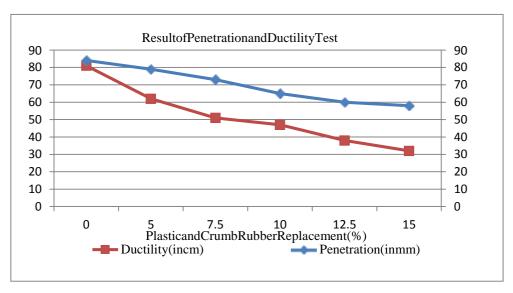


Fig. 2: Result of penetration and ductility test

Comment: After replacement of plastic and crumb rubber with bitumen, there is decrease in penetration & ductility value which indicates that the bitumen is getting harder with more plastic and rubber replacement.


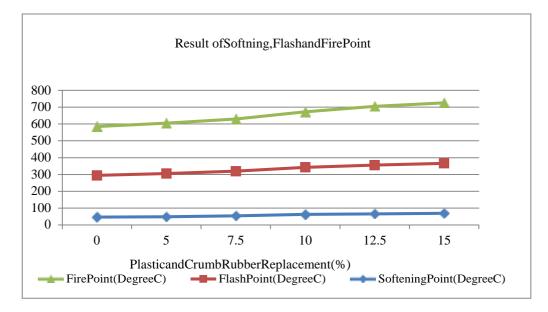


Fig. 3: Result of softening, flash and fire point

Comment: With an increase in plastic and crumb rubber percentage, there is an increase in flash, fire and softening point which indicates more susceptibility of bitumen in tropical regions.

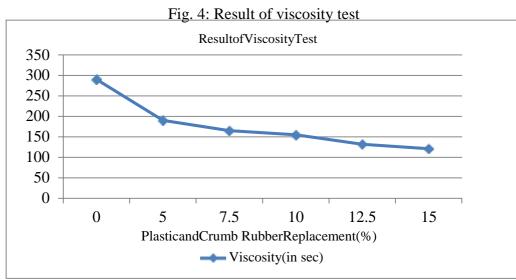

Comment: Reduction of viscosity is useful to lower the mixing and compaction temperature of the asphalt.

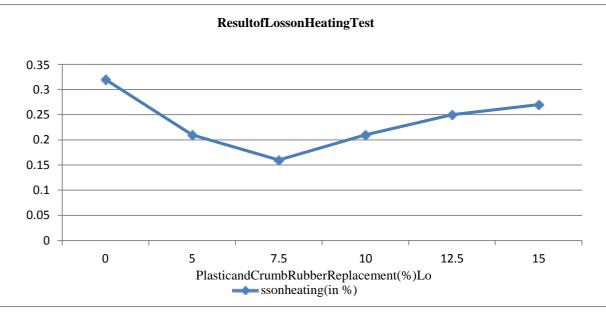


Fig. 5: Result of loss on heating test

Comment: Addition of plastic and crumb rubber shows a slight decrease in loss on heating.

4.3 Laboratory tests on bituminous mixes

The results of various tests conducted on bituminous mixes are as follows:

| S no. | Tes | Specification Result | | Standard Value | | | | |
|-------|-------------------|----------------------|---------|----------------|--|--|--|--|
| | t | | | | | | | |
| 1. | Marshal Stability | Pure Bitumen | 610 kg | Minimum | | | | |
| | Test (Stability) | 10% Replacement | 990 kg | 340 kg | | | | |
| 2. | Marshal Stability | Pure Bitumen | 8.7 mm | Min 8 mm | | | | |
| | Test (flow value) | 10% Replacement | 10.9 mm | Max 17 mm | | | | |
| 3. | Compressive | Pure Bitumen | 820 kg | Min 700 kg | | | | |
| | strength of | 10% Replacement | 1620 | | | | | |
| | | | | | | | | |

 Table 6: Result of tests on bituminous mixes

Section A-Research paper

| | bitumen | | kg | |
|----|------------------|-----------------|--------|------------|
| 4. | Indirect tensile | Pure Bitumen | 340 kg | Min 330 kg |
| | strength of | 10% Replacement | 620 kg | |
| | bitumen | | | |

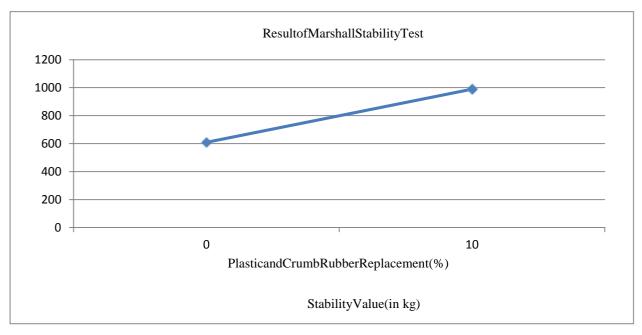


Fig. 6: Result of Marshall Stability test

Comment: Addition of plastic and crumb rubber shows increase in stability value which is useful to sustain large load.

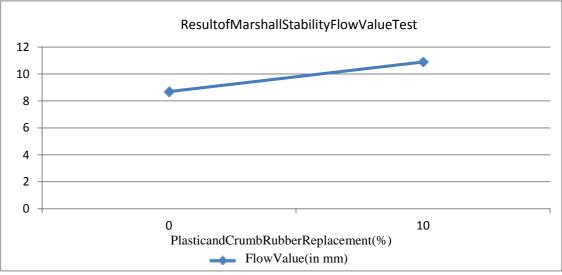


Fig. 7: Result of Marshall Stability flow value test

Comment: Replacement of plastic and crumb rubber shows an increase in flow value i.e. less resistance to deformation but change is very little which is in specified limit.

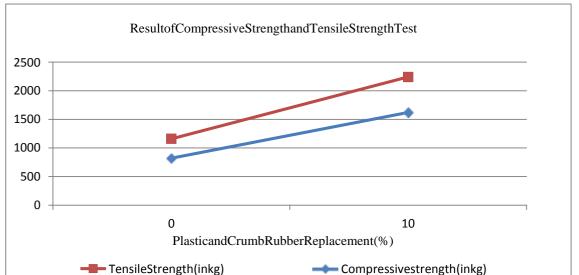


Fig. 8: Result of compressive strength and tensile strength test

Comment: Addition of plastic and crumb rubber shows increase in compressive and tensile strength.

5. CONCLUSION

Based upon the work carried out in the project, the following conclusions can be framed:

- 10% of plastic coating samples showed more strength than conventional bitumen.
- By studying the test results of the conventional bitumen and the waste plastic and crumb rubber modified bitumen it is concluded that the penetration value and the softening value of the conventional bitumen can be improved significantly.
- By studying the test results of the conventional bitumen and the waste plastic and crumb rubber modified bitumen it is concluded that the flash point and the fire point of the conventional bitumen can be improved significantly.
- Plastic and crumb rubber as a 10% replacement in bitumen can be used as an optimum percentage value for bituminous mix design and testing.
- 10% plastic and crumb rubber replacement in bitumen shows better results for pavement properties.
- Plastic with crumb rubber can be utilized as a partial blending material in design of flexible pavement.
- It can be used as a partial replacement in bitumen as well as coating over aggregate.

6. REFERENCES

- Dr C. E. G. Justo, Dr S. K. Khanna, Dr A. Veeraragavan, "Highway Engineering" (NemChand & Bros., Roorkee, 2015), PP. 339-380.
- [2] S.Rajasekaran, Dr R. Vasudevan, Dr Samuvel Paulraj, "Reuse of waste plastics coated aggregates-Bitumen Mix composite for Road Application – Green Method", American Journal of Engineering Research, 2013, PP. 1-13.
- [3] Dr S D Khandekar, Sasane Neha B., Gaikwad. Harish and Dr J R Patil, "Application of Waste Plastic as an Effective Construction Material in Flexible Pavement", submitted To International Research Journal of Engineering and Technology (IRJET), 2015, PP. 1943-1948.
- [4] Shirish N. Nemade and Prashant V. Thorat, "Utilization of Polymer Waste for Modification of Bitumen in Road Construction", Scientific Reviews and Chemical Communications, Volume 2, Issue 3, 2013, PP. 198-213.
- [5] Mohd Rasdan Ibrahim Herda Yati Katman, Mohamed Rehan Karim, Suhana Koting, and Nuha S.

Mashaan," A Review on the Effect of Crumb Rubber Addition to the Rheology of Crumb Rubber Modified Bitumen", Advances in Materials Science and Engineering Volume 2013, Article ID 415246, 8 page.

- [6] Abhaykumar.S.W, Mudassi.D.W, (2013),"Use of Waste Plastic and Waste Rubber in Aggregate and Bitumen for Road Materials ", International Journal of Emerging Technology and Advanced Engineering, Volume 3, Issue 7, PP- 301.
- [7] Apurva J C,(2013),"Use Of Plastic Waste In bituminous Pavements",International Journal Of Application Or Innovation In Engineering And Management, Vol. 2, Issue 4,PP .540-552
- [8] Mohamed.O.S, .Maciej.S and Jozef.H,(2013)"New Study on Improved Performance of Paving Asphalts by Crumb Rubber and Polyethylene Modification", Material Science Engg, Volume 2, Issue 4.
- [9] Prasad K.V.R, Mahendra.S.P, Kumar.N.S, (2013)"Study on Utilization of Pet (Polyethylene Terephthalate) Waste in Bituminous Mixes", IJECT, Vol. 4, Issue Spl 1.
- [10] Rema devi M, Leni.S, Mini M.I.,(2013) ,Reduction of optimum bitumen content in bituminous mixes using plastic coated aggregates, International Journal of Innovative Research in Science, Engineering and Technology,Vol. 2, Issue 3.
- [11] Harpalsinh Raol, Abhijitsinh Parmar, Jitendra Jayswal, Dhaval Patel, (2014), "Effect of the use of Crumb rubber in conventional bitumen on the Marshall Stability value", IJRET, Vol 3, Issue 1.
- [12] "Mrs.Vidula Swami Et.al, "Use of waste plastics in construction of bituminous road", International journal of engineering and sciences and technology (IJEST), ISSN: 0975-5462, Vol.4, May 2012, 2351-2355
- [13] "Aydin Kavak Et.al," In situ modification of road material using a special polymer" Scientific research and essays, ISSN: 1992-2248, Vol.5 (17), pp.2547-2555, 4th September, 2010.
- [14] "Rokade S, " Use of waste plastics and waste rubber tires in bituminous highway pavements", 2012 International conference on Future environments and Energy, IPCBEE Vol.28(2012), IACSIT Press, Singapore.
- [15] "Gayle and King Et.al, "polymer modified Bitumen", Third International Road Federation, Middle East Regional Meeting, Riyadh, Saudi Arabia, February 1998.
- [16] "Sinan Hinislioglu Et.al, "Use of High Density Waste Polyethylene as a bitumen modifier." Materials Letters 58(2004)267-271, Science Direct.
- [17] "R. Vasudevan Et.al," Proceedings of the International Conference on Sustainable Solid Waste Management, 5 7 September 2007, Chennai, India. Pp.105-111
- [18] Y.Adnan.,H.Arshad.,I.Muhammad.,A.Anwaar.,2014.Performance Evaluation of AsphalticMixtures Using Bakelite .Life Science Journal2014;11(7s).[6] Dwivedi.A., Mattoo.M., Prabhu.J.,Dwivedi.A.,Jain.P.,2014.A Survey on Cost Comparison of Sustainable Plastic Road with Regular BitumenRoad,IJIRSET.2017,p.0602011.
- [19] D. H. M. Jassim, O. T.Mahmood, and S. A. Ahmed, "Optimum use of plastic waste to enhance the Marshall properties and moisture resistance of Hot Mix Asphalt," International Journal of Engineering Trends and Technology, vol. 7, no. 1, pp. 18–25, 2014.
- [20] Venkatesh, K., Swarup, A. and Mishra, U., 2021.Performance Analysis of Waste Plastic ModifiedBitumen for Pavements. RESEARCH REVIEWInternational Journal of Multidisciplinary,
- [21] Hake, S., Damgir, R. and Awsarmal, P., 2020.Utilization of Plastic waste in Bitumen Mixes For bituminous Pavement. Transportation ResearchProcedia, 48, pp.3779-3785.
- [22] Yadav.A, Chandrakar.R, Construction of plastic roads: An effective way to utilize wastes , IRJET,Impact Factor value: 6.171,2017.

- [23] Appiah, J., Berko-Boateng, V. and Tagbor, T.,2017. Use of waste plastic materials for road construction in Ghana. Case Studies inConstruction Materials, 6, pp.1-7.
- [24] Awoyera, P. and Adesina, A., 2020. Plastic Wastes to construction products: Status, limitations and future perspective. Case Studies In Construction Materials, 12, p.e00330.
- [25] Abd El-Rahman, A., El-Shafie, M., Mohammedy, M. and Abo-Shanab, Z., 2018. Enhancing the performance of blown asphalt binder using waste EVA copolymer (WEVA). Egyptian Journal of Petroleum, 27(4), pp.513-521.
- [26] Bansal, S., Kumar Misra, A. and Bajpai, P., 2017. Evaluation of modified bituminous concrete mix developed using rubber and plastic waste materials. International Journal of SustainableBuilt Environment, 6(2), pp.442-448
- [27] Ghulam Sakhi, A. and Amit, G., 2018. Use of Waste Plastic, Waste Rubber and Fly Ash in Bituminous Mixes. Indian Journal of Science And Technology,
- [28] P.B.Rajmane, A.K.Gupta, D.B.Desai. EffectiveUtilization of Waste Plastic In Construction Ofbituminous Pavement For Improving TheirPerformance, IOSR-JMCE PP: 27-30.[17]
- [29] Chada Jithendra Sai Raja et al. (2020). A Reviewon Use of Plastic in Construction of Roads. J. ofAdvancement in Engineering and Technology,V7I4.01.[18]
- [30] R.Manju et al . Use of Plastic Waste inBituminous Pavement. International Journal ofChemTech Research, 2017,pp:804-811.[19]
- [31]Noor, A. and Rehman, M., 2022. A mini-review on the use of plastic waste as a modifier of the bituminous mix for bituminous pavement. CleanerMaterials, 4, p.100059.[20]
- [32] Huda Shafiq and Anzar Hamid, 2016. PlasticRoads: A Recent Advancement in WasteManagement. International Journal ofEngineering Research and, V5(09).